

## EFFECT OF STRAIN RATE ON MICROSTRUCTURE OF A LOW CARBON STEEL WIRE

Reçu le 09/03/2008 – Accepté le 21/07/2011

### Résumé

L'importance commerciale des aciers au carbone faiblement alliés est due à leurs propriétés de déformation plastique. Ces propriétés de déformation permettent à ces aciers d'être fabriqués sous forme de fils. Cette étude concerne un acier destiné au tréfilage, produit par Trifisoud-Setif –Algerie sous forme de barres et contient (%poids) 0.05%C, 0.3%Mn, 0.1%S et 0.12%Cr. L'analyse par microscopie optique et microscopie électronique à balayage (SEM) est utilisée pour identifier la microstructure du matériau dans les conditions de réception avant et après la déformation. Il a été mis en évidence que les propriétés mécaniques dépendent du taux de tréfilage ( $\tau_w$ ). Les températures de recristallisation et la taille du grain sont déterminées et varient avec  $\tau_w$ .

**Mots clés:** Acier à bas carbone, déformation, tréfilage, microstructure, recristallisation.

### Abstract

The commercial importance of low alloy carbon steels is due to their plastic deformation properties. These properties allow them to be formed into useful shapes such as wires. The present steel is produced by Trifisoud-Setif –Algeria and used for wiring. It is a low carbon steel wire containing mainly (weight %) 0.05%C, 0.3%Mn, 0.1%S and 0.12%Cr and is supplied as rods. The optical microscopic and SEM analyses are used to identify the microstructure of the material in as received and deformed conditions. It is found that tensile properties depend on the wire drawing area reduction ( $\tau_w$ ). The annealing temperatures and the grain size are determined; they also vary with  $\tau_w$ .

**Keywords:** Low carbon steel, deformation, wire drawing, microstructure, recrystallization.

H. BOUHALAIS  
Z.LAROUK

Laboratoire de  
Microstructures et Défauts  
dans les Matériaux.  
Département de Physique  
Université Mentouri  
Constantine- Algérie

ملخص

- Trifisoud

. 0.12%Cr 0.3%Mn, 0.1%S, 0.05%C ( )

(SEM)

. $\tau_w$

.( $\tau_w$ )

**I**ntroduction

The wiredrawing process deals with tension tests in which a rod is stretched. The wire length is increased while its cross section area is reduced. It is a convenient way to shape materials with an increase in hardening. It is well known that plastic deformation involves in wiredrawing increases the density of dislocation. These dislocations, in turn, increase the yield strength of the material [1-2].

The presence of inclusions is very harmful for the wiredrawing process [3]. Gagné and Thibault [4] studied the effect of inclusion size, number, shape, distribution, and composition in hot rolling cast steel billets. Their results suggested that there is relationship between inclusion deformability and composition. They concluded that the number and size of inclusions must be at minimum level and need to be as deformable as possible in steel designed for wiredrawing.

Plastic strain given to the metal before annealing has a profound effect on the recrystallized grain size. Generally, higher strain produces smaller grain size. This effect is well explained by the process of recrystallization which depends on the rate of grain nucleation and growth [5].

**1. Experimental procedure**

The material is received in long rods with different diameters of 6, 4, 3.18 and 2.45 mm and produced by Trifisoud, Setif, Algeria". The chemical composition (weight %) is shown in table (1).

C	Mn	Si	S	P	Ni	Cr	Cu
0.05	0.3	0.1	0.025	0.02	0.12	0.12	0.12

**Table 1**

The material is formed using a wiredrawing machine BREITENBACH type Standard 1R/4VZ. The access speed is 3.79 m/s and the out one is 9 m/s, the process is carried out at room temperature using a soap of silicate as a lubricant and tungsten carbide dies.

The reduction of area by wiredrawing ( $\tau_w$ ) is calculated as follow:

$$\tau_w = \left[ 1 - \left[ \frac{d_2}{d_1} \right]^2 \right] \times 100 \quad (1)$$

Where  $d_2$  is the final wire diameter and  $d_1$  is the initial one. Optical Metallography examination, using a ZEISS microscope equipped with AXIO-VISION software used for image analysis, is carried out on samples after grinding, polishing and etching in a solution of 2% concentrated nitric acid in ethanol. The polished samples are also used for hardness measurements, which were made using a Vickers hardness testing, LEITZ type, at 2Kg load. The measurements are taken from five different indentations. Prior ferrite grain size measurements are carried out on five different images using the three circle technique [6]. Scanning Electron Microscope (SEM) TESCAN type, equipped with energy dispersive X ray (EDAX), is used. Tensile machine type of ZWICK, of 100 KN as a maximum weight, is used with a deformation rate of 2 mm/min piloted by PC. Specimens for tensile testing are machined from rods and each one have 150mm of length, tensile tests are carried out at room temperature up to fracture.

An annealing of wiredrawing specimens is carried out at different temperatures for different holding times. The total recrystallization temperatures are determined for different  $\tau_w$ ; samples are then quenched in water (table 2).

$\tau_w$ (%)	55.5	72	83
$T_{rec}$ (°C)	520	500	480
$t_{rec}$ (min)	300	420	1020

**Table 2**

**2. Results and discussion**

The optical microscopic analyses, in as received conditions, show that the material before deformation has a homogenous structure of equiaxed ferrite and pearlite with 11µm of grain size. However, as a result of deformation these grains are elongated in the direction of

Wiredrawing process (Figs.1a, b and c).

show essentially similar character. The failure is ductile with a pronounced necking for all wires (Fig.2).

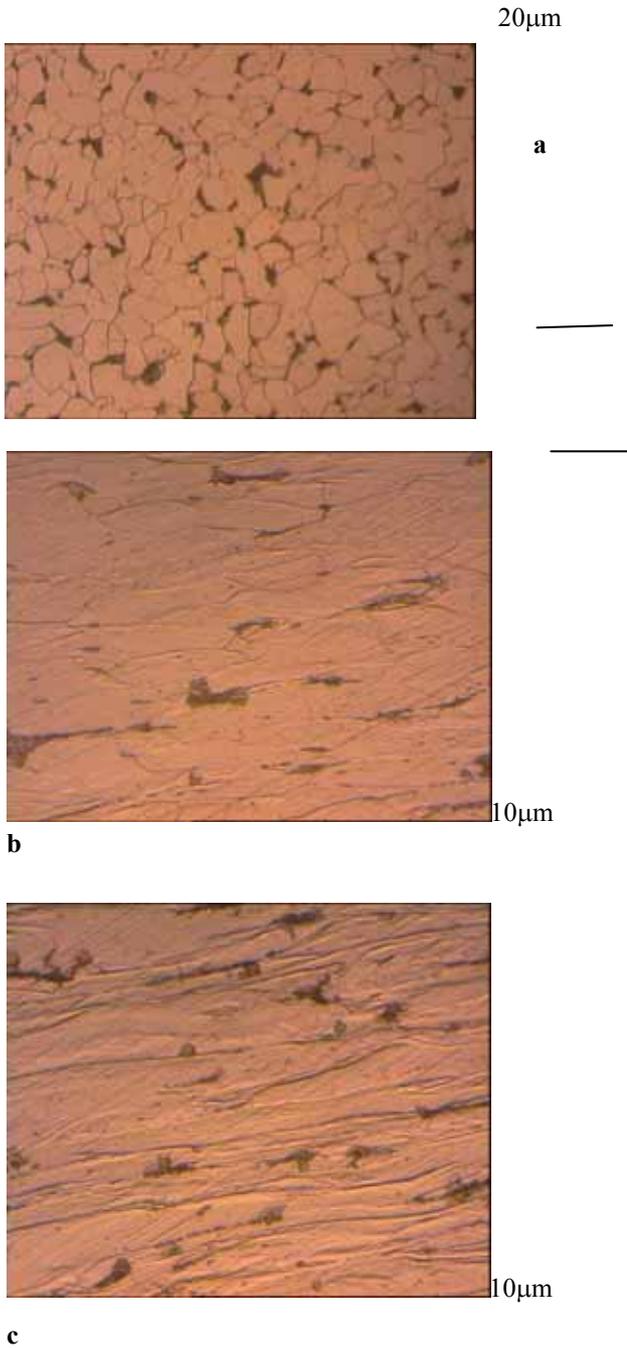


Figure 1 : Optical micrographs of the material in as received conditions: a)  $\phi = 6\text{mm}$ , b)  $\phi = 3.18\text{mm}$ , c)  $\phi = 2.45\text{mm}$ .

The strength and hardness of the material in as-received conditions are taken as the base strength of the wire. The tensile tests for all specimens, in as received conditions or deformed prior to testing,

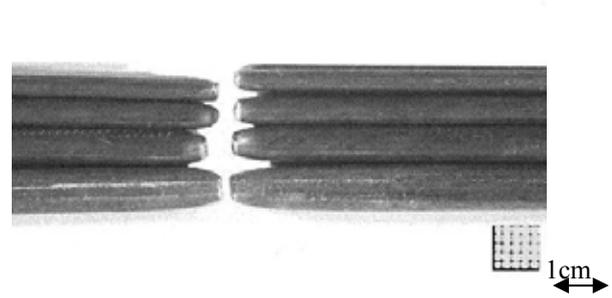


Figure 2 : Optical micrograph showing the ductile failure of the material.

The results are presented in table (3). It can be seen that the tensile properties vary with initial wire diameter prior to testing. The relatively low rupture ductility ( $\epsilon_r$ ) for the material indicates that there is significant effect of reduction of area prior to testing, due to wiring process. Table 3 also shows the increase of yield strength ( $R_e$ ) and the strength tensile ( $R_m$ ) as a function of the area reduction ( $\tau_w$ ).

$\phi$ (mm)	$\tau_w$ (%)	Hv (Kgf/mm <sup>2</sup> )	$R_e$ (N/mm <sup>2</sup> )	$R_m$ (N/mm <sup>2</sup> )	$\epsilon_r$ (%)
06	-	122	176.8	370.7	28
04	55.5	222	537.2	613.1	18
3.18	72	229.6	696.7	709.0	22
2.45	83	250.5	713.1	742.0	22

Table 3


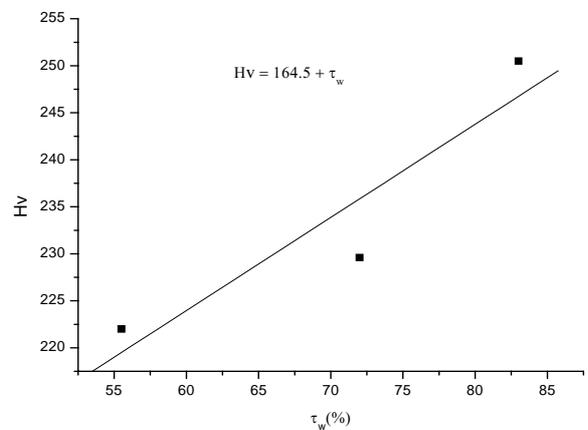


Figure 3 : Hardness as a function of  $\tau_w$  in as received conditions


## EFFECT OF STRAIN RATE ON MICROSTRUCTURE OF A LOW CARBON STEEL WIRE

This variation is a direct consequence of the increase of dislocation density generated after the wire drawing process. However, similar results are observed with the increase of hardness (Hv) versus  $\tau_w$  (Fig.3.). This figure shows a linear relationship between Hv and  $\tau_w$ . Generally, the hardness of the material increases with strain hardening due to plastic deformation and additional elements (substitutional and/or interstitial)[7]. These elements and grain boundaries play an important part in interacting with dislocations and inhibiting their movement.

SEM examination of the polished cross section in as – received conditions reveals the presence of inclusions which are flat/elongated and distributed at random directions (Fig.4 a and b.).

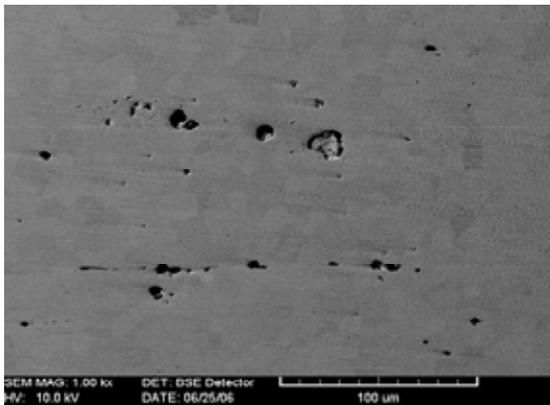

(a)

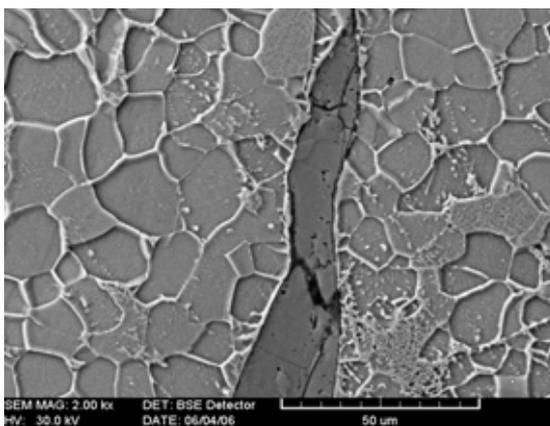

(b)

Figure 4: SEM Micrographs (a and b) of polished samples showing the presence of inclusions.

This figure ( Fig.4b.) also shows that the cohesion of the inclusions to the matrix is not entire. The weak link

between inclusions and the matrix acts as preferable sites for nucleation and growth of micro cracks. These inclusions are also found in fractured surface (Fig.5).

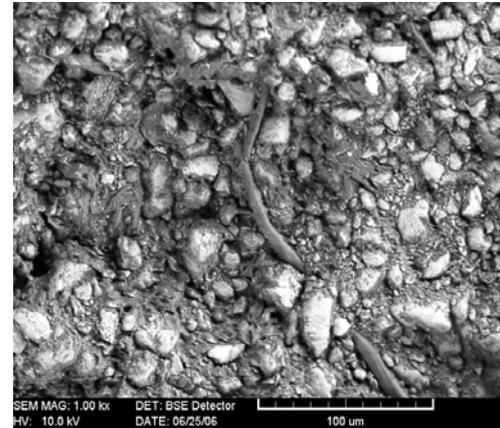


Figure 5 : SEM Micrograph of fractured surface showing the presence of inclusions.

The EDAX analysis shows that the inclusions are iron oxide (magnetite) [8]. The average diameter of these inclusions ( $D_i$ ) is about 10  $\mu\text{m}$  and the ratio  $D_i/D_w$  of the present steel is very low. The reduction per pass of this steel is expected to be quiet high since Tandon et al. [3] found that maximum reduction per pass is inversely proportional to the  $D_i/D_w$ .

During plastic deformation energy is stored in the material in the form of dislocations. The process of recrystallization allows it to be released [9].

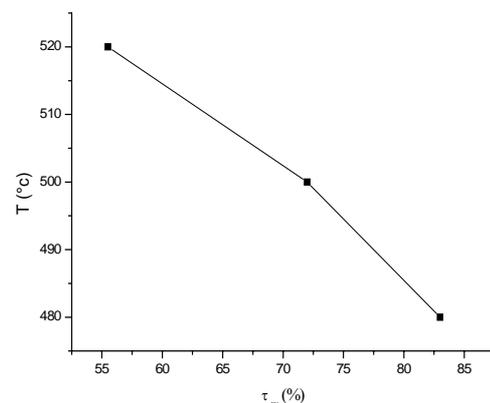


Figure 6 :Total recrystallisation temperature as a function of area reduction  $\tau_w$ .

Wiredrawing process followed by recrystallization at different temperatures for different annealing times is needed in order to soft the deformed material. Hence, the total recrystallized wires show severe loss in bulk hardness (Table 4). It has been found that the increase of the cold working accelerated the softening of the CP-Ti isothermally annealed [10]. Figure 6 shows that the recrystallization temperature decreases with the increase of the area reduction. The process of wiredrawing raises the multiplication of sites necessary for new grains nucleation.

$\tau_w$ (%)	55.5	72	83
$Hv_{rec}$ (Kgf/mm <sup>2</sup> )	102	110	120
$d_{rec}$ ( $\mu$ m)	8	7	5

**Table 4**

The heat treatments of recrystallization are chosen carefully and led to a drastic softening without producing coarse grains ( less than 11 $\mu$ m) , i.e result in grain refinement of the structure (Table 4). Figure 7 shows the variation of the hardness of the recrystallized wires ( $Hv_{rec}$ ) versus inverse root square of corresponding grain sizes ( $d_{rec}$ (mm) ). It can be noted that this plot is similar to Petch and Hall relationship [11]. A linear relationship is observed between  $Hv_{rec}$  and  $d_{rec}$ . This relationship permits to estimate the hardness of the material for a given recrystallized grain size. However, it necessary to note that the slope of this relationship for Ti alloy is much lower than (about 0.22) the slope of the present material [11].

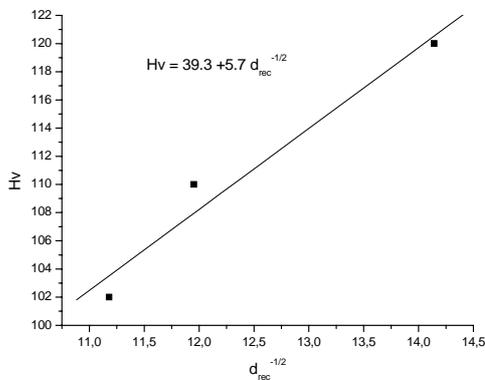


Figure 7: Hardness of recrystallized material versus  $d_{rec}^{-1/2}$

**CONCLUSION**

It is appropriate to sum up the objectives of this study and its achievements

- It has been demonstrated that the initial microstructure is ferrite-pearlite with 11  $\mu$ m ferrite grain size for the non deformed material. Moreover, the steel contains inclusions with small diameter (about 10 $\mu$ m).
- The wiredrawing process increases material strength.
- Annealing Process results in drastic softening of the material and producing a smaller grain size.
- A linear relationship between  $Hv_{rec}$  and  $d_{rec}$  is established and is the type of :  

$$Hv_{rec} = 39.3 + 5.7 d_{rec}^{-1/2}$$

**REFERENCES**

[1] G. E.Dieter, ” Mechanical Metallurgy” 3rd Edition , McGraw Hill book company, 1986, pp197-198.

[2] J.Philibert, A.Vignes, Y. Beéchet, and P;Combrade "Métallurgie du minerai au matériau", Ed. Masson, Paris, 1998, pp. 776-776

[3] S. Tandon, S. p. Deshmukh, R. S. Mishra, and K.Krishnamurthy and R. Tayloe, " Fracture criteria prediction in wiredrawing using finite element modeling", Wire Journal International, January, 2006, pp58-62.

[4] M.Gagné and E. Thibault, "Control of inclusion characteristics in direct cast steel billets", Canad..Met. Quarterly., vol. 38, N°5, 1999, pp. 311-321

[5] A. Cottrell "An introduction to metallurgy" ,ELBS Arnold, 2<sup>nd</sup> Edition , London, 1982.

[6] "ASTM Standard Designation“ E112-88.,1994, book of ASTM standard, vol.301, ASTM, Philadelphia, P, A 1997, pp227.

[7] B.Yalamanshili, P.M.Power, and D.Landham, “A technical review of industrial practices for decreasing the strain hardening rate of low carbon steel”, Wire Journal International, July 2005, pp108-111.

[8] H.Bouhalais and Z.Larouk " Microstructure characterisation of a low carbon steel wire" JMSM2006, Meknès, 24-26 Novembre 2006, pp. 272

[9] R.W.K. Honeycombe "The Plastic deformation of metals", Edward Arnold Ltd., London, 1994

[10] F.M. Guclu and H. Cimenoglu "The Recrystallization Behaviour Of CP-Titanium", Materials Science Forum Vols. 467-470, 2004, pp.459-464.

[11] J.Philibert, A.Vignes, Y. Beéchet, and P; Combrade, " Métallurgie du minerai au matériau", Ed. Masson, Paris, 1998, pp768-769.